

Mn²⁺ doped Single Crystals of Cd K₂ (SO₄)₂ · 6H₂O: Spectroscopic and Local Structure Studies

Ram Kripal

Designation & Department: Prof., Physics

Institution: University of Allahabad, Prayagraj-211002, Uttar Pradesh, India

ORCID: 0000-0002-3483-8704

Abstract

The splitting parameters of zero field of the Mn²⁺ doped Cd K₂ (SO₄)₂·6H₂O (CKS) single crystals are computed utilizing the superposition model. The estimated parameters agree well with those obtained from EPR. The conclusion of experiment that the Cd²⁺ site is replaced by the Mn²⁺ ion in CKS is confirmed by theoretical study. The crystal's optical spectra are obtained employing crystal field parameters obtained from the superposition model and crystal field analysis program. A fair correspondence is found with the experimental band positions. Thus, the experimental observations are verified by the theoretical calculations.

Keywords: Inorganic compounds, Electron paramagnetic resonance, Zero field splitting, Single crystal, Crystal fields, Superposition model.

Date of Submission: 12-08-2026

Date of acceptance: 24-08-2026

I. Introduction

EPR studies yield information on the nature of the site into which the impurity ion enters and its symmetry [1-2]. EPR of Mn²⁺ impurity has been widely studied in different single crystals due to sensitivity of its zero field splitting values to small structural distortions in the lattice [3-5].

The superposition model (SPM) is used generally to model the crystal field (CF) and zero field splitting (ZFS) parameters for use in many other studies [6–10]. SPM and the point-charge model [11, 12, 13] are largely used to find the parameters of the crystal field (CF). SPM was proposed for CF under certain assumptions [14]. Finding a static spherical polar coordinate system (R_L, θ_L, Φ_L) for each ion or ligand from the host crystal's X-ray structural data is important for doing an SPM analysis on the CF. Mismatches of ionic charge, ionic size and inter-ionic bonding are likely to yield some local distortion when transition metal ions are doped. Critical analysis of experimental spin-Hamiltonian parameters for Mn²⁺ and Fe³⁺ in CaO and MgO crystals has been performed [15] providing the SPM parameters and showing that the CF for 3d ions satisfies the superposition principle. SPM intrinsic parameters based on reliable ligand distances have been estimated for the alkali earth oxides, [16].

The general formula A₂⁺ B²⁺ (XO₄)₂ · 6H₂O crystals are known as Tutton single crystals where A is a monovalent cation, B is a divalent cation (usually a transition metal ion) and X is sulfur or selenium [17–18]. Tutton crystals are famous isostructural crystal family having the same monoclinic symmetry, the space group P2₁/a and two formula units per unit cell Z=2 [19]. Tutton crystals (salts) are valuable crystals because they are used widely in UV filters [20].

Cadmium potassium sulfate hexahydrate crystals (CKS) are crystallized in the monoclinic crystal system and belong to the Tutton crystalline salts family. Having suitable crystal sizes, high purity and small transparency in the UV region, they could be the potential candidates for optoelectronic devices [21]. Cadmium sulfate (CdSO₄) has various uses, including electroplating, pigment production, and as a component in batteries and solar cells [22]. Potassium sulfate is dominantly used as a fertilizer. It is preferred for the crops like tobacco and some fruits and vegetables. [23]. It is sometimes used as an alternative blast media similar to soda in soda blasting [24]. Cadmium potassium sulfate is likely related to the individual uses of its constituent compounds.

EPR study of Mn²⁺ doped CKS has been done at 298 K and the spin-Hamiltonian parameters have been obtained [25]. From angular variation studies, it is concluded that magnetic [Mn (H₂O)₆]²⁺ complexes are created when the Mn²⁺ ion enters the divalent sites of the Tutton salt lattice. The a*bc axis system, where a* is perpendicular to b and c, (crystal axes) is used to discuss the orientations. The angular variation of the spectrum indicated that the crystal field symmetry is orthorhombic.

In the present study, the ZFS parameters D and E are estimated for the Mn²⁺ ion in CKS at 298 K (room temperature, RT) taking CF parameters from SPM and perturbation equations [26]. The objective is to locate the position of Mn²⁺ ion and the distortion taking place in the CKS crystal. The results for the Mn²⁺ ion at the

substitutional Cd²⁺ site in CKS crystal with local distortion provide good agreement with the EPR experimental values. Further aim of the study is to find the extent to which CF theory and SPM technique can be applied to Mn²⁺ ions in CKS crystals in order to produce an SPM parameter database. This will determine molecular nanomagnet (MNM) design and computer simulation of their magnetic and spectroscopic properties. The transition ion-based MNM class currently includes single-molecule magnets (SMM) [27], single-chain magnets (SCM) [28], and single ion magnets (SIM) [29]. Due to interesting magnetic properties of MNM, such as magnetization's macroscopic quantum tunneling and possible uses in high-density information storage and quantum computing, the above systems have attracted large attention from scientists and researchers [27, 28]. There are various synthesized SCM or SMM systems with Mn²⁺ and Cr³⁺ ions [30]. Due to the fact that model calculations for simpler crystal systems can be used as a basis for more complex ones, the parameters of the model obtained in this case may be used for ZFS parameter calculations for Mn²⁺ ions at appropriate sites in MNM. This work's modeling can be extended to get various crystals of scientific and industrial value in a number of other ion-host systems.

II. Crystal Structure

The crystal structure of Tutton salt CKS is monoclinic with space group P 2₁/a [31], isomorphous with cadmium ammonium sulphate (CAS). The unit cell's parameters are: Z = 2, β = 106.86°, a = 9.433, b = 12.823 and c = 6.286 Å. All other divalent cations in the unit cell are in general positions, with the two inequivalent ones located at points (0, 0, 0) and (1/2, 1/2, 0). Water molecules form a slightly warped octahedron around each divalent cation. The other Tutton salts exhibit the same pattern of bond length, with the Cd-O(8) and Cd-O(7) bonds being larger than the Cd-O(9) bond. Figure 1 shows the symmetry-adapted axis system (SAAS) and CKS crystal structure.

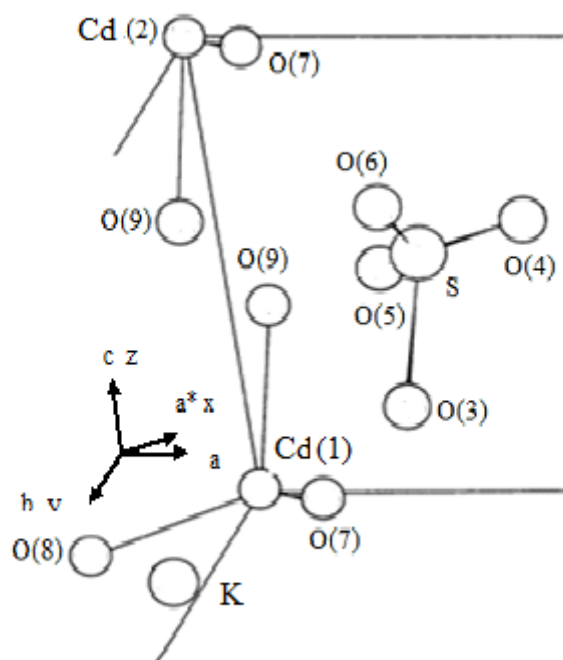


Fig. 1. The room-temperature CKS crystal structure and the symmetry-adapted axis system (SAAS).

III. Crystal Field and Zero Field Splitting Parameter Calculations

The EPR spectrum may be analyzed with the spin Hamiltonian [7]:

$$E(S_x^2 - S_y^2) + D\left\{S_z^2 - \frac{1}{3}S(S+1)\right\} + \mu_B B.g.S = \mathcal{H}(1)$$

where B, μ_B , g, D and E are the applied magnetic field, Bohr magneton, splitting factor, second rank axial, and second rank rhombic ZFS parameters [32–33]. Figure 1 shows the laboratory x, y, and z axes as well as the

a*, b, and c modified crystallographic axes (a* is normal to axes b and c). The directions of metal-ligand bonds being mutually perpendicular are referred to as the symmetry **adapted** axes (SAA) or the local symmetry axes of the site. As shown in Fig.1, the axis-Z of SAAS is along the crystal axis- c, and (X, Y) are perpendicular to the axis-Z. When Mn²⁺ ions are doped in CKS crystal, they occupy Cd²⁺(1) sites with some local distortion in the lattice [34].

The Mn²⁺ ion spin Hamiltonian is given as [35],

$$\mathcal{H}_o + \mathcal{H}_{so} + \mathcal{H}_{ss} + \mathcal{H}_c = \mathcal{H} \quad (2)$$

$$\mathcal{H}_c = \sum B_{kq} C_q^{(k)} \quad (3)$$

where B_{kq}, in Wybourne notation, represent the CF parameters and C_q^(k), the spherical tensor operators. B_{kq} ≠ 0 in the orthorhombic symmetry crystal field only for k = 2, 4; q = 0, 2, 4. Using SPM, the CF parameters B_{kq} in CKS are calculated [35].

The symmetry of the local field about Mn²⁺ ions in CKS crystal is orthorhombic (OR-type I) [7], where the ZFS parameters D and E are evaluated as follows [36]:

$$D = \left(\frac{3\zeta^2}{70P^2D'} \right) [-B_{20}^2 - 21\zeta B_{20} + 2B_{22}^2] + \left(\frac{\zeta^2}{63P^2G} \right) [-5B_{40}^2 - 4B_{42}^2 + 14B_{44}^2] \quad (4)$$

$$E = \left(\frac{\sqrt{6}\zeta^2}{70P^2D'} \right) [2B_{20} - 21\zeta] B_{22} + \left(\frac{\zeta^2}{63P^2G} \right) [3\sqrt{10}B_{40} + 2\sqrt{7}B_{44}] B_{42} \quad (5)$$

Here G = 10B + 5C, D' = 17B + 5C, P = 7B + 7C. B and C provide Racah parameters and ζ, the spin-orbit coupling parameter. Utilizing average covalency parameter N, B = N⁴B₀, C = N⁴C₀, ζ = N²ζ₀, where ζ₀ gives free ion spin-orbit coupling parameter and B₀ and C₀ are Racah parameters for free ion [35, 37]. ζ₀ = 336 cm⁻¹, B₀ = 960 cm⁻¹ and C₀ = 3325 cm⁻¹ for free Mn²⁺ ion [7].

The covalency parameter N is found from N = (√B/B₀ + √C/C₀)/2 using Racah parameters (B = 857 cm⁻¹, C = 2977 cm⁻¹) obtained from optical study of Mn²⁺ ion in CKS [38].

The CF parameters using SPM are evaluated [14, 36], with co-ordination factor K_{kq}(θ_j, φ_j) and intrinsic parameter $\overline{A}_k(R_j)$, as

$$B_{kq} = \sum_j K_{kq}(\theta_j, \phi_j) \overline{A}_k(R_j) \quad (6)$$

$\overline{A}_k(R_j)$ is obtained from

$$\overline{A}_k(R_0) \left(\frac{R_0}{R_j} \right)^{t_k} = \overline{A}_k(R_j) \quad (7)$$

where the ligand's distance from the dⁿ ion is denoted by R_j, $\overline{A}_k(R_0)$ is the intrinsic parameter, R₀ is the reference distance of the ligand from the metal ion and t_k gives power law exponent. For Mn²⁺ doped crystals, t₂ = 3 and t₄ = 7 [36]. Since the co-ordination about Mn²⁺ ion is octahedral, $\overline{A}_4$ is calculated from the relation [39]

$$\overline{A}_4(R_0) = \frac{3}{4} Dq \quad (8)$$

From optical study [38], Dq = 740 cm⁻¹. Therefore, $\overline{A}_4(R_0) = 555$ cm⁻¹. For 3d⁵ ions the ratio $\frac{\overline{A}_2}{\overline{A}_4}$ falls in the range 8 - 12 [35, 40-41]. With $\overline{A}_2 = 10 \overline{A}_4$, $\overline{A}_2 = 5550$ cm⁻¹.

IV. Results and Discussion

Using the ligand configuration around Mn²⁺ ion shown in Fig. 1 and SPM, the CF parameters of the Mn²⁺ ion at the Cd²⁺(1) sites are estimated. Table 1 gives atoms' coordinates in CKS single crystal with bond length R (with and without distortion) and angles θ , ϕ for site I. The ZFS and CF parameters as well as R₀, reference distance is given in Table 2. Table 2 shows that R₀ = 0.200 nm being slightly less than the sum of radii of ions (0.223 nm) of Mn²⁺ = 0.083 nm and O²⁻ = 0.140 nm with no distortion give ZFS parameter values at octahedral substitutional site I to be different from the EPR experimental ones [25]. Experimental parameters of ZFS |D| and |E| (10⁻⁴ cm⁻¹) for site I from EPR are 309.4, 75.0, respectively. |E|/|D| is obtained as 0.242 being smaller than the standard value 0.33 [33]. |D| and |E| found theoretically without distortion are larger than the EPR experimental values. The value of |E|/|D| is also larger than the standard value 0.33 [33]. Hence, local distortion is introduced into calculation. Using above value of R₀ and local distortion, the ZFS parameter values for substitutional octahedral sites I are in good match with the EPR experimental ones [25]. The parameters t₂ = 3 and t₄ = 7 with transformation S2 for standardization [33] are used to obtain |E|/|D| ratio near to 0.33 and calculated ZFS parameters very close to experimental values from EPR.

Table 1. Atoms' coordinates, bond length R (with and without distortion) and angles θ , ϕ in CKS single crystal (site I).

Mn ²⁺ Position	Ligands	Ligands'spherical polar co-ordinates								
		x	y	z	R(nm)θ ⁰			φ ^o		
					(Å)					
		Without distortion								
Site : Substitutional Cd(1) (0.0000, 0.0000, 0.0000)	O7	0.1839	0.1149	0.1745	0.22977	R ₁	85.64	θ ₁	85.40	φ ₁
	O8	-0.1730	0.1200	0.0336	0.22968	R ₂	89.16	θ ₂	94.32	φ ₂
	O9	0.0001	-0.0760	0.3210	0.22405	R ₃	81.76	θ ₃	90.00	φ ₃
	O7'	-0.1839	-0.1149	-0.1745	0.22977	R ₄	94.35	θ ₄	94.60	φ ₄
	O8'	-0.1839	0.3851	0.6745	0.70454	R ₅	84.51	θ ₅	91.50	φ ₅
	O9'	0.1839	0.6149	0.3255	0.82041	R ₆	87.73	θ ₆	88.71	φ ₆
		With distortion								
I	O1				0.28492		66.64		86.90	
	O2				0.29348		71.16		92.32	
	O3				0.28406		62.76		88.00	
	O4				0.29327		85.35		90.60	
	O5				0.78954		82.51		91.50	
	O6				0.90541		89.73		90.71	

Table 2. The Mn²⁺ doped CKS crystal's CF and ZFS parameters.

ZFS CF parameters (cm ⁻¹)		parameters (10 ⁻⁴ cm ⁻¹)							
Site	R ₀ (nm)	B ₂₀	B ₂₂	B ₄₀	B ₄₂	B ₄₄	D	E	E / D
Without distortion									
Site I									
$\frac{A_2}{A_4} = 10$	0.200	-14763.7	-18221.8	2420.828	2574.151	4824.854	2262.4	1164.2	0.514
With distortion									
Site I									
$\frac{A_2}{A_4} = 10$	0.200	-6449.77	3179.051	-6.06927	75.69374	2669.833	309.4	102.9	0.332
							Exp.	309.4	75.0 0.242

The CFA computer program [42] and B_{kq} parameters (with distortion) are used to calculate the optical spectra of Mn²⁺ doped CKS single crystals. By diagonalizing the full Hamiltonian, the Mn²⁺ ion's energy band positions are computed.

Table 3 gives the energy band positions (experimental and calculated) for substitutional site I [38].

Table 3. Both calculated and experimental Energy bands of single crystal of CKS doped Mn²⁺.

Transition from ⁶ A _{1g} (S) state (cm ⁻¹)	Band experimental	Band calculated
		I
⁴ T _{1g} (G)	18868	23612, 23628, 23776, 23845, 24041, 24110
⁴ T _{2g} (G)	23042	24241, 24256, 24502, 24541, 24582, 24625
⁴ A _{1g} (G)	24875	24937, 24966
⁴ E _g (G)	24950	24970, 24978, 24988, 25000
⁴ T _{2g} (D)	28163	26769, 26824, 27205, 27268, 28834, 28843
⁴ E _g (D)	29940	29332, 29374, 29885, 29969
⁴ T _{1g} (P)	31746	30406, 30478, 31484, 31512, 35234, 35345
⁴ A _{2g} (F)		38648, 38759
⁴ T _{1g} (F)		40610, 40707, 40751, 40896, 40969, 40985

It is observed from Table 3 that the calculated and experimental energy band positions agree reasonably well. Therefore, the theoretical results verify the EPR experimental one [25, 38] that Mn²⁺ ions enter the CKS crystal at substitutional Cd²⁺(1) octahedral site. The model parameters found may be utilized in ZFS parameter calculations for Mn²⁺ ions at similar molecular nano magnet sites.

V. Conclusions

To find the splitting parameters of zero field, the superposition model and perturbation theory are applied for CKS single crystals doped with Mn²⁺ ions. The obtained ZFS parameters match well with the experimental values from EPR. The calculated positions of the optical energy bands correspond reasonably well with those from the experiment. Therefore, the experimental finding that Mn²⁺ ions replace Cd²⁺ (1) sites in CKS is confirmed by the theoretical investigation. The model parameters estimated in this study may be utilized for ZFS parameter determinations for Mn²⁺ ions at appropriate sites in MNM. The above modeling technique may be useful in finding different crystals of various scientific and industrial applications.

Acknowledgement

The author is grateful to the Head of Physics Department of Allahabad University, Allahabad for providing facilities of the department and to Prof. C. Rudowicz of Faculty of Chemistry, Adam Mickiewicz University, Poznan, Poland for CFA program.

Declarations

Ethical Approval:

There were no human or animal subjects in this study, and it wasn't conducted in any protected or private locations. Corresponding locations did not require any special permissions.

Competing interests:

The author affirms that no known conflicting financial interests or personal relationships could have influenced any of the work presented in this paper.

Funding:

There is no funding received..

Availability of data and materials:

Upon request, the data will be made available.

References

- [1]. M. Fidan, H. Icbudak, R. Tapramaz, Y. Sahin, Thermal and EPR spectroscopic studies of novel coordination compound *trans*-bis(acesulfamato)tetraaquazinc(II) with Mn(II) impurity, *Spectrochim. Acta Part A Mol.Biomol. Spectrosc.* 79 (2011) 17–20.
- [2]. B. Natarajan, S. Mithira, P. Sambasiva Rao, Identification of symmetry, structure and defects of dopant Mn(II) ions in Zn(C₃H₃O₄)₂(H₂O)₂ by single crystal EPR technique, *Solid State Sci.* 10 (2008) 1916–1923.
- [3]. J. A. Weil, J. R. Bolton, *Electron Paramagnetic Resonance: Elementary Theory and Practical Applications*; 2nd ed., Wiley, New York, 2007.
- [4]. S. P. Rathee, S. S. Hooda, EPR and superposition-model analysis of zero-field splitting parameters for Mn²⁺ doped in ZnNbOF₅·6H₂O and CoNbOF₅·6H₂O single crystals, *Indian J. Phys.* 99(1)(2025)145-148.
- [5]. D. Halder, Y. Jana, D. Piwowarska, P. Gnutek, C. Rudowicz, Tailoring single-ion magnet properties of coordination polymer C₁₁H₁₈DyN₃O₉ (Dy-CP) using the radial effective charge model (RECM) and superposition model (SPM), *Phys. Chem. Chem. Phys.* 26(2024) 19947-19959.
- [6]. C. Rudowicz, P. Gnutek, M. Açıkgöz, Superposition model in electron magnetic resonance spectroscopy – a primer for experimentalists with illustrative applications and literature database, *Appl. Spectrosc. Rev.* 54 (2019) 673–718.
- [7]. A. Abragam, B. Bleaney, *Electron Paramagnetic Resonance of Transition Ion*, Dover, New York, 1986.
- [8]. J.R. Pilbrow, *Transition-Ion Electron Paramagnetic Resonance*, Clarendon Press, Oxford, 1990.
- [9]. B.G. Wybourne, *Spectroscopic Properties of Rare Earth*, Wiley, New York, 1965.
- [10]. J. Mulak, Z. Gajek, *The Effective Crystal Field Potential*, Elsevier, Amsterdam, 2000.
- [11]. R. Bo'ca, Zero-field splitting in metal complexes, *Coord. Chem. Rev.* 248 (2004) 757–815.
- [12]. M. G. Brik, N. M. Avram (Eds.). *Optical Properties of 3d-Ions in Crystals: Spectroscopy and Crystal Field Analysis*. Heidelberg: Springer, (2013), Y. Y. Yeung: Chapter 3, pp. 95-121.
- [13]. A. K. Yadav, U. M. Tripathi, and R. Kripal, Theoretical Calculation of Zero-Field Splitting Parameters for Mn²⁺ in Potassium Hydrogen Sulphate, *Appl. Magn. Reson.* 53 (2022) 941–947.
- [14]. D. J. Newman and B. Ng, The superposition model of crystal fields, *Rep. Prog. Phys.* 52 (1989) 699-763.
- [15]. D. J. Newman, E. Siegel, Superposition model analysis of Fe³⁺ and Mn²⁺ spin-Hamiltonian parameters, *J. Phys. C: Solid State Phys.* 9 (1976) 4285-4292.
- [16]. Y. Y. Yeung, Local distortion and zero-field splittings of 3d⁵ ions in oxide crystals, *J. Phys. C: Solid State Phys.* 21 (1988) 2453-2462.
- [17]. F. Bosi, G. Belardi, P. Ballirano, Structural features in Tutton's salts K₂[M²⁺(H₂O)₆](SO₄)₂, with M²⁺=Mg, Fe, Co, Ni, Cu, and Zn, *Am. Mineral.* 94(2009) 74–82.
- [18]. M. Wildner, D. Marinova, D. Stoilova, Vibrational spectra of Cs₂Cu(SO₄)₂·6H₂O and Cs₂Cu(SeO₄)₂·nH₂O (n=4, 6) with a crystal structure determination of the Tutton salt Cs₂Cu(SeO₄)₂·6H₂O, *J. Mol. Struct.* 1106(2016) 440–51.
- [19]. H.T. Montgomery, E.C. Lingafelter, The crystal structure of Tutton's salts. II. Magnesium ammonium sulfate hexahydrate and nickel ammonium sulfate hexahydrate *Acta Cryst.* 17(1964) 1478–9.
- [20]. M. de Oliveira, S. Ghosh, T. S. Pacheco, G. J. Perpétuo, C. J. Franco, Growth and structural analysis of ammonium nickel cobalt sulfate hexahydrate crystals, *Materials Research Express* 4(2017) 105036.
- [21]. A. Abu El-Fadl, A. M. Nashaat, Growth, structural, and spectral characterizations of potassium and ammonium zinc sulfate hydrate single crystals, *Appl. Phys. A* 123 (2017) 339(11 pages).
- [22]. D. R. Lide, ed. *CRC Handbook of Chemistry and Physics* (87th ed.), Boca Raton, CRC Press, Florida, 2006.
- [23]. United Nations Industrial Development Organization, International Fertilizer Development Center, *Fertilizer manual* (3rd ed.), Kluwer Academic, Dordrecht, Netherlands, 1998.
- [24]. Super K (Potassium Sulphate), American Surface Prep. Archived from the original on 9 December 2014, Retrieved 7 December 2014.
- [25]. V. K. Jain, EPR of Mn²⁺ in Tutton Salts, *Z. Naturforsch.* 32 a(1977) 1364-1367.
- [26]. W. L. Yu, M.G. Zhao, Spin-Hamiltonian parameters of ⁶S state ions, *Phys. Rev. B* 37(1988)9254-9267.
- [27]. G. Aromí, E. K. Brechin, Synthesis of 3d metallic single-molecule magnets, *Struct. Bonding* 122 (2006) 1-67.
- [28]. C. Coulon, H. Misayaka, R. Clérac, Single-Chain Magnets: Theoretical Approach and Experimental Systems, *Struct. Bonding* 122 (2006) 163-206.
- [29]. M. Murrie, Cobalt(II) single-molecule magnets, *Chem. Soc. Rev.* 39 (2010) 1986-1995.
- [30]. C. van Wüllen, Magnetic anisotropy through cooperativity in multinuclear transition metal complexes: theoretical investigation of an anisotropic exchange mechanism, *Mol. Phys.* 111 (2013) 2392–2397.
- [31]. H.T. Montgomery, E.C. Lingafelter, The Crystal Structure of Tutton's Salts. IV. Cadmium Ammonium Sulfate Hexahydrate, *Acta Cryst.* 20(1966)728-730.
- [32]. C. J. Radnell, J. R. Pilbrow, S. Subramanian, M. T. Rogers, Electron paramagnetic resonance of Fe³⁺ ions in (NH₄)₂SbF₅, *J. Chem. Phys.* 62(1975) 4948-4952.
- [33]. C. Rudowicz, R. Bramley, On standardization of the spin Hamiltonian and the ligand field Hamiltonian for orthorhombic symmetry, *J. Chem. Phys.* 83(1985) 5192- 5197.
- [34]. B. N. Figgis, M. A. Hitchman, *Ligand Field Theory and its Applications*; Wiley, New York, 2000.

- [35]. T. H. Yeom, S. H. Choh, M. L. Du, M. S. Jang, EPR study of Fe³⁺ impurities in crystalline BiVO₄. Phys. Rev. B 53(1996) 3415-3421.
- [36]. T. H. Yeom, S. H. Choh, M. L. Du, A theoretical investigation of the zero-field splitting parameters for an Mn²⁺ centre in a BiVO₄ single crystal. J. Phys.: Condens. Matter 5(1993) 2017-2024.
- [37]. C. K. Jorgensen, Modern Aspects of Ligand Field Theory; North- Holland, Amsterdam, 1971, p.305.
- [38]. N. Satyanarayana, S. Radhakrishna, Electronic Absorption Spectra of Mn²⁺ Ion in Cd(NH₄)₂(SO₄)₂ · 6H₂O and CdK₂(SO₄)₂ · 6H₂O Single Crystals, Physica 138B (1986) 97-102
- [39]. D. J. Newman, B. Ng (Eds.), Crystal Field Handbook; Cambridge University Press, Cambridge, 2000.
- [40]. A. Edgar, Electron paramagnetic resonance studies of divalent cobalt ions in some chloride salts. J. Phys. C: Solid State Phys. 9(1976) 4303-4314.
- [41]. R. Kripal, M. G. Misra, A. K. Yadav, P. Gnutek, M. Açıkgöz, C. Rudowicz, Theoretical Analysis of Crystal field Parameters and Zero field Splitting Parameters for Mn²⁺ ions in Tetramethylammonium Tetrachlorozincate, Polyhedron, 235(2023)116341.
- [42]. Y. Y. Yeung, C. Rudowicz, Crystal Field Energy Levels and State Vectors for the 3d^N Ions at Orthorhombic or Higher Symmetry Sites. J. Comput. Phys. 109(1993)150-152.